

1 **WO<sub>3</sub>-TiO<sub>2</sub> based catalysts for the simulated solar radiation assisted**  
2 **photocatalytic ozonation of emerging contaminants in a municipal**  
3 **wastewater treatment plant effluent**

4  
5 **A. Rey<sup>1\*</sup>, P. García-Muñoz<sup>1</sup>, M.D. Hernández-Alonso<sup>2</sup>, E. Mena<sup>1</sup>, S. García-**  
6 **Rodríguez<sup>3</sup>, F.J. Beltrán<sup>1</sup>**

7  
8 <sup>1</sup>*Departamento de Ingeniería Química y Química Física, Universidad de Extremadura, Av. Elvas*  
9 *s/n, 06006 Badajoz (Spain)*

10 <sup>2</sup>*División de Energía Renovable, CIEMAT, Av. Complutense 40, 28040 Madrid (Spain)*

11 <sup>3</sup>*Instituto de Catálisis y Petroleoquímica, CSIC, Av. Marie Curie, 2, 28049 Madrid (Spain)*

12  
13 **Abstract**

14 This work is focused on the use of TiO<sub>2</sub>-WO<sub>3</sub> photocatalysts for the removal of a  
15 mixture of emerging contaminants through photocatalytic ozonation using simulated  
16 solar light as radiation source. Own-made TiO<sub>2</sub>-WO<sub>3</sub> catalysts with WO<sub>3</sub> content around  
17 4 wt.% were synthesized using P25 and titanate nanotubes as TiO<sub>2</sub> starting materials.  
18 Photocatalysts were thoroughly characterized by means of ICP-OES, N<sub>2</sub> adsorption-  
19 desorption isotherms, XRD, TEM, Raman, XPS and DR-UV-Vis spectroscopy.  
20 Photocatalytic ozonation using WO<sub>3</sub> based titanate nanotubes composite gave place to  
21 complete removal of emerging contaminants (caffeine, metoprolol and ibuprofen in a  
22 Municipal Wastewater Treatment Plant effluent aqueous matrix) in less than 40 min  
23 with TOC removal up to 64% after 2 h. The highest catalytic activity of this material in  
24 the reaction under study compared to bare TiO<sub>2</sub> is due to several effects such as higher  
25 activity under visible light radiation joined to an increase in adsorption capacity of  
26 organic compounds and catalytic ozonation ability caused by the presence of WO<sub>3</sub>.

27  
28 **Keywords**

29 Photocatalytic ozonation, tungsten oxide-titanium dioxide, titanate nanotubes, ozone,  
30 emerging contaminants

## 1 1. Introduction

2 Emerging contaminants (ECs), such as pharmaceuticals and personal care products,  
3 which usually present endocrine disrupting activity, are frequently detected in  
4 wastewater and aquatic environments [1,2]. These contaminants can cause severe  
5 adverse effects in human and wildlife and their removal is of a great concern on  
6 environmental and health risk management [2,3]. However these compounds are  
7 hardly biodegradable so they are not removed by conventional treatment at municipal  
8 wastewater treatment plants (MWWTPs), and therefore advanced treatment  
9 technologies are required [1].

10 Advanced oxidation processes (AOPs) which involve the formation of highly reactive  
11 species such as hydroxyl radical ( $\text{HO}^\bullet$ ), have demonstrated their efficiency to degrade  
12 many ECs transforming them into harmless products [4]. Among these AOPs,  
13 photocatalytic ozonation, i.e. the combination of photocatalytic oxidation and ozone  
14 processes, can greatly enhance the rates of ECs degradation and, specially, the  
15 mineralization achieved by the single processes [5,6,7]. In fact, a synergistic effect has  
16 been observed between ozone and irradiated photocatalyst due to both the strong  
17 electron trapping effect of ozone, that avoids, to some extent, the electron-hole  
18 recombination process, and to the reaction of ozone with the superoxide ion radical  
19 ( $\text{O}_2^{\bullet-}$ , intermediate species in photocatalytic reactions). In these two steps the ozonide  
20 ion radical ( $\text{O}_3^{\bullet-}$ ) is generated and further transformed into  $\text{HO}^\bullet$ , thus increasing the  
21 concentration of this highly reactive species in the aqueous medium [5,8,9].

22 One of the most important aspects in the application of photocatalytic wastewater  
23 treatment technologies is the cost derived from the radiation source operation and  
24 maintenance. The use of solar energy as radiation source avoids this drawback leading  
25 to more economic technologies [10]. However, most of the photocatalytic ozonation  
26 studies conducted to date make use of  $\text{TiO}_2$  as photocatalyst that only uses around 5%  
27 of solar radiation (UV range). Different methods to solve this limitation, mainly applied  
28 to ozone-free photocatalytic oxidation processes, have been developed, such as ion  
29 doping, modification of  $\text{TiO}_2$  surface with noble metals, metal ion implantation or  
30 coupling semiconductors [10,11]. In this line, composite materials of coupled  $\text{WO}_3$  and  
31  $\text{TiO}_2$  semiconductors can extend the absorption of radiation to the visible region as a  
32 result of the lower band gap energy of  $\text{WO}_3$  (around 2.7 eV), and also allow a wide  
33 electron-hole separation avoiding recombination to some extent [11].  $\text{TiO}_2$ - $\text{WO}_3$   
34 coupled semiconductors have been successfully applied to the degradation of different  
35 organic contaminants in water through photocatalytic oxidation under visible light  
36 radiation [12,13,14,15,16]. In addition, these materials combined with gold  
37 nanoparticles have also been tested for photocatalytic ozonation of model compounds  
38 such as oxalic acid and TNT giving place to promising results [17,18].

39 This work has been focused on the use of different  $\text{TiO}_2$ - $\text{WO}_3$  composite catalysts to  
40 extend the radiation absorption to visible light and make better use of the solar  
41 emission spectrum in photocatalytic ozonation process applied to wastewater  
42 detoxification. Two different  $\text{TiO}_2$  supports, commercial  $\text{TiO}_2$  P25 and own-made  
43 titanate nanotubes, which present very different textural and structural properties, have

1 been used. The synthesized materials were tested in photocatalytic ozonation of  
2 ibuprofen (IBP), metoprolol (MTP) and caffeine (CAF) in a spiked municipal wastewater  
3 effluent from a secondary treatment and using simulated solar light as radiation. These  
4 contaminants, IBP, a nonsteroidal anti-inflammatory drug for pain relief and fever  
5 reduction; MTP, a  $\beta$ -blocker used for several cardiovascular diseases; and CAF, a  
6 stimulant drug mainly from coffee consumption, have been selected because of their  
7 frequent presence in municipal wastewater [2].

## 8 9 **2. Experimental section**

### 10 **2.1. Catalysts preparation**

11 Aeroxide TiO<sub>2</sub> P25 (anatase/rutile 80/20, 21 nm crystal size) was used as the starting  
12 photocatalytic material. The procedure to obtain titanate nanotubes catalyst (NT) has  
13 been reported in previous works [19,20]. Briefly, 1 g of the precursor P25 was  
14 hydrothermally treated at 130°C in 70 mL of 10 M NaOH in a Teflon-lined autoclave,  
15 during 48 h. The mixture was stirred for 30 min before and after the thermal treatment.  
16 In a second stage, the obtained powders were thoroughly washed using diluted HCl.  
17 The powders were recovered from the solutions by centrifugation, dried at 100°C  
18 overnight and then calcined in air atmosphere for 3 h at 350°C.

19 P25 and NT photocatalysts were coated with nanosized WO<sub>3</sub> particles (P25-WO<sub>3</sub> and  
20 NT-WO<sub>3</sub> samples) as described elsewhere [18]. First 0.216 g H<sub>2</sub>WO<sub>4</sub> were added in  
21 100 mL of ultrapure water and then aqueous ammonia solution was added drop wise  
22 until the tungstic acid was completely dissolved. Further 5 g of P25 or NT were added  
23 under continuous stirring and the obtained mixture was stirred for 30 min and then  
24 acidified to pH 4 with 0.5 M HCl. Then 10 mL of an aqueous solution of oxalic acid 0.1  
25 M was added to the mixture and stirred for 1 h at 40°C to prevent the aggregation of  
26 WO<sub>x</sub> particles in the precipitate. Finally the solid was recovered by filtration, dried at  
27 110°C for 2 h and then calcined in air atmosphere for 2 h at 420°C. The TiO<sub>2</sub>-WO<sub>3</sub> thus  
28 prepared had a theoretical amount of WO<sub>3</sub> of 3.8 wt.%. For comparative purposes, NT  
29 photocatalyst was also calcined in air atmosphere for 2 h at 420°C (sample NT-T).

### 30 31 **2.2. Characterization**

32 Total tungsten content of the catalysts was analyzed by inductively coupled plasma  
33 with an ICP-OES Optima 3300DV (Perkin-Elmer) after acidic microwave digestion of  
34 the samples.

35 BET surface area and pore volume of the photocatalysts were determined from their  
36 nitrogen adsorption–desorption isotherms obtained at -196°C using an Autosorb 1  
37 apparatus (Quantachrome). Prior to analysis the samples were outgassed at 250°C for  
38 12 h under high vacuum ( $<10^{-4}$  Pa).

39 The crystalline phases present in the photocatalysts were inferred from their X-ray  
40 diffraction (XRD) patterns recorded using a powder Bruker D8 Advance XRD

1 diffractometer with a Cu K $\alpha$  radiation ( $\lambda=0.1541$  nm). The data were collected from  
2  $2\theta=20^\circ$  to  $80^\circ$  at a scan rate of  $0.02$  s $^{-1}$  and 1 s per point.

3 A JEM-2100F 200 kV transmission electron microscope (JEOL Ltd.) and a TEM Tecnai  
4 G20 Twin 200 kV transmission electron microscope (FEI Company) were used to study  
5 the crystallinity and morphology of the samples.

6 Raman spectra were obtained using a Nicolet Almega XR Dispersive micro-Raman  
7 (Thermo Scientific) with a spectral resolution of  $2$  cm $^{-1}$ . The samples were excited at  
8  $633$  nm with the laser beam power at 100% and 200 scans accumulation.

9 X-ray photoelectron spectra (XPS) were obtained with a K $\alpha$  Thermo Scientific  
10 apparatus with an Al K $\alpha$  ( $h\nu=1486.68$  eV) X-ray source using a voltage of  $12$  kV under  
11 vacuum ( $2\times 10^{-7}$  mbar). Binding energies were calibrated relative to the C1s peak from  
12 carbon samples at  $284.6$  eV. The resulting XPS peaks were curve-fitted to a  
13 combination of Gaussian and Lorentzian functions using a Shirley type background for  
14 peak analysis.

15 Diffuse reflectance UV-Vis spectroscopy (DR-UV-Vis) measurements, useful for the  
16 determination of the semiconductor band gap, were performed with an UV-Vis-NIR  
17 Cary 5000 spectrophotometer (Varian-Agilent Technologies) equipped with an  
18 integrating sphere device.

19

### 20 **2.3. Catalytic activity measurements**

21 Ibuprofen sodium salt (IBP), metoprolol tartrate (MTP) and caffeine (CAF) were used  
22 as target contaminants to test the catalytic activity of the synthesized materials. They  
23 were added to a real municipal wastewater effluent (MWW) taken from Badajoz  
24 MWWTP (Badajoz, Spain) designed for 225,000 inhabitants with an average inlet flow  
25 of  $37,500$  m $^3$  day $^{-1}$ . Effluents were collected downstream of the MWWTP secondary  
26 biological treatment, filtered and stored at  $-20^\circ\text{C}$  until use.

27

28 Photocatalytic experiments were carried out in semi-batch mode in a laboratory-scale  
29 system consisting of a  $0.5$  L glass-made spherical reactor, provided with a gas inlet, a  
30 gas outlet and a liquid sampling port. The reactor was placed in the chamber of a  
31 commercial solar simulator (Suntest CPS, Atlas) provided with a  $1500$  W air-cooled Xe  
32 arc lamp with emission restricted to wavelengths over  $320$  nm because of the presence  
33 of quartz, glass and polyester cut-off filters. The irradiation intensity was kept at  $550$  W  
34 m $^{-2}$  and the temperature of the system was maintained between  $25$  and  $35^\circ\text{C}$   
35 throughout the experiments. If required, a laboratory ozone generator (Anseros  
36 Ozomat Com AD-02) was used to produce a gaseous ozone-oxygen stream that was  
37 fed to the reactor. In that case, the ozone concentration was recorded on an Anseros  
38 Ozomat GM-6000Pro gas analyzer. A scheme of the experimental set-up is depicted in

39 **Fig.1.**

40

1 In a typical photocatalytic ozonation experiment, the reactor was first loaded with 0.5 L  
2 of an aqueous solution containing 2 mg L<sup>-1</sup> of ECs initial concentration in the MWW  
3 effluent. Then, 0.25 g of the catalyst were added and the suspension was stirred in the  
4 darkness for 30 min while bubbling air to the system. After this dark stage, the lamp  
5 was switched on and, simultaneously, a mixture of ozone-oxygen (10 mg L<sup>-1</sup> ozone  
6 concentration) was fed to the reactor at a flow rate of 20 L h<sup>-1</sup>. The irradiation time for  
7 each experiment was 2 h. Samples were withdrawn from the reactor at intervals and  
8 filtered through a 0.2 µm PET membrane to remove the photocatalyst particles.

9  
10 Experiments of adsorption (i.e., absence of radiation and ozone), photolysis (i.e.,  
11 radiation in absence of catalysts and ozone), photocatalytic oxidation (i.e., radiation  
12 and catalyst in absence of ozone), ozonation (i.e., absence of radiation and catalyst),  
13 catalytic ozonation (i.e., absence of radiation) were also carried out for comparative  
14 analysis. In addition, photocatalytic oxidation experiments of IBP were carried out  
15 under visible radiation using a polyester wavelength cut-off filter below 390 nm.

16  
17 ECs concentrations were analyzed by high-performance liquid chromatography HPLC-  
18 DAD (Hitachi, Elite LaChrom) using a Phenomenex C-18 column (5 µm, 150 mm long,  
19 3 mm diameter) as stationary phase and 0.5 mL min<sup>-1</sup> of acetonitrile-acidified water  
20 (0.1% H<sub>3</sub>PO<sub>4</sub>) as mobile phase (from 5% to 60% in acetonitrile) during 25 min and 10  
21 min re-equilibration time). Identification and quantification was carried out at 220 nm.  
22 Total organic carbon (TOC) and inorganic carbon (IC) were measured using a  
23 Shimadzu TOC-V<sub>SCH</sub> analyzer. Aqueous ozone concentration was measured by  
24 following the indigo method using an UV-Visible spectrophotometer (Evolution 201,  
25 Thermospectronic) set at 600 nm [21]. Ozone concentration in the gas phase was  
26 continuously monitored by means of an Anseros Ozomat GM-6000Pro analyzer.  
27 Finally, chemical oxygen demand (COD) was determined by means of the dichromate  
28 method, using Dr. Lange cuvette test; biological oxygen demand (BOD<sub>5</sub>) was analyzed  
29 by a respirometric method using an Oxitop® WTW system; aromaticity as the  
30 absorbance of the sample at 254 nm and phosphates by means of colorimetric method  
31 using a Merck Spectroquant kit (UV-Visible spectrophotometry, Evolution 201 from  
32 Thermospectronic).

### 34 **3. Results and discussion**

#### 35 **3.1. Characterization of the photocatalysts**

36 **Table 1** summarizes tungsten content, some textural parameters, band gap energy  
37 and absorption edge wavelength of the photocatalysts. It can be seen that the W mass  
38 composition (expressed as WO<sub>3</sub>) of the TiO<sub>2</sub>-WO<sub>3</sub> catalysts was close but somewhat  
39 higher to the nominal value expected (3.8 wt.%).

40 **Fig.2** shows N<sub>2</sub> adsorption-desorption isotherms where it can be noticed that P25  
41 based catalysts are non-porous materials with type II isotherms whereas NT catalysts  
42 presented type IV isotherms with H3 hysteresis loops characteristics of mesoporous  
43 solids, according to IUPAC classifications [22]. On the other hand, the incorporation of

1 W did not change the isotherm aspect of these photocatalysts respect their supports.  
2 Main differences are observed for NT catalysts where the incorporation of W procedure  
3 has changed the slope and shifted the hysteresis loop in NT-WO<sub>3</sub> respect to NT,  
4 indicating a lower porosity. This is mainly related to the heat-treatment applied, as can  
5 be deduced from the similarity of the isotherms of NT-T and NT-WO<sub>3</sub>. Calcination at  
6 420°C triggers structural changes as discussed below [20]. From these analyses,  
7 specific surface area ( $S_{\text{BET}}$ ) and pore volume ( $V_{\text{PORE}}$ ) were calculated (see **Table 1**). As  
8 can be observed P25 based catalysts show  $S_{\text{BET}}$  values according to that indicated by  
9 the supplier for P25 (around 50 m<sup>2</sup>g<sup>-1</sup>), and similar pore volume around 0.25 m<sup>3</sup>g<sup>-1</sup>.  
10 Thus, the incorporation of W and calcination of the composite material does not  
11 significantly affect its textural properties. On the other hand, NT presented higher  $S_{\text{BET}}$   
12 and pore volume, according to its mesoporous structure as it was previously reported  
13 for similar materials [20]. In this case, the incorporation of W has favoured a decrease  
14 in the surface area and pore volume of the NT-WO<sub>3</sub> catalyst mainly due to the  
15 calcination step, although some pore blockage after W deposition cannot be  
16 disregarded according to the lower values of textural parameters of this catalyst  
17 respect to the NT-T sample.

18 Structural characterization of the photocatalysts was accomplished by means of XRD,  
19 TEM and Raman analyses and results are depicted in **Fig.3** to **Fig.5**, respectively. P25  
20 based catalysts gave place to similar XRD patterns with main diffraction peaks  
21 attributable to anatase and rutile TiO<sub>2</sub> phases. The absence of peaks attributable to W  
22 species could be due to the low content in the catalysts and/or to the high dispersion of  
23 W. This was also confirmed, as **Fig.4** shows, by TEM micrographs where W particles  
24 were undistinguishable. In addition, heat-treatment applied to P25-WO<sub>3</sub> photocatalyst  
25 does not produce any significant change in the TiO<sub>2</sub> structure. Regarding NT  
26 photocatalyst, a shifted diffraction peak position at 24.9° respect to 25.4° for anatase is  
27 observed, indicating titanate structure [20]. TEM micrograph confirmed nanotubular  
28 morphology for NT sample (**Fig.4**). On the other hand, the incorporation of W in NT-  
29 WO<sub>3</sub> photocatalyst led to a transformation of the titanate structure into anatase as  
30 evidenced by the shift of the corresponding diffraction peaks (e.g. most intense from  
31 24.9° to 25.3°) join to an increase in their intensity. This transformation is mainly related  
32 to the calcination step at 420°C as the XRD pattern and TEM micrograph of the NT-T  
33 sample subjected to the same heat-treatment confirmed, and also according to results  
34 reported elsewhere [20]. TEM micrographs corroborated the transformation of titanate  
35 nanotubular structures to elongated anatase particles (**Fig.4**). **Fig.5** shows Raman  
36 spectra of TiO<sub>2</sub>-WO<sub>3</sub> photocatalysts. In **Fig.5 (a)** vibration peaks at 395, 517 and 638  
37 cm<sup>-1</sup> were observed in both catalysts (P25-WO<sub>3</sub> and NT-WO<sub>3</sub>) which are  
38 unambiguously attributed to anatase phase of TiO<sub>2</sub> [23,24]. On the other hand, only for  
39 P25 based material, rutile phase is observed as a broad peak at 448 cm<sup>-1</sup> according to  
40 the P25 structural composition [23,24]. These results also confirmed the transformation  
41 of titanate structure into anatase after calcination step [20]. The lowest intensity  
42 observed in the Raman spectra for the anatase vibrations can be related to the lowest  
43 crystallinity of NT-WO<sub>3</sub> photocatalyst according to XRD results [23]. On the other hand,  
44 **Fig.5 (b)** shows main W contributions to the Raman spectra. The band located around  
45 792 cm<sup>-1</sup> corresponds to weak second-order feature of anatase assigned to the first

1 over-tone band at  $395\text{ cm}^{-1}$  [25]. At around  $954\text{ cm}^{-1}$  appears another contribution  
2 assigned to the stretching mode of the terminal W=O bond which is characteristic of  
3 two-dimensional tungsten oxide surface species  $\text{WO}_x$  [25,26]. In addition, the weak  
4 band located at around  $1042\text{ cm}^{-1}$  could be related to the presence of  $\text{WO}_x$  species in  
5 tetrahedral coordination [27]. The observed contributions at  $954$  and  $1042\text{ cm}^{-1}$   
6 together with the absence of any signal close to  $800\text{ cm}^{-1}$  suggest that nothing of the  
7 added W contributes to the formation of crystalline  $\text{WO}_3$  [27]. These results are in a  
8 good agreement with XRD and TEM observations. Again it is noteworthy the lowest  
9 intensity of the NT- $\text{WO}_3$  spectrum as commented above.

10 Surface chemical composition of the catalysts was analysed by XPS. Full spectra are  
11 depicted in **Fig.6 (a-d)** and confirmed the presence of O, Ti and C in all the samples (O  
12 1s, Ti 2p and C 1s peaks). In addition, the peaks of W 4d and W 4f spectral regions  
13 appear in the full spectra of the  $\text{TiO}_2$ - $\text{WO}_3$  photocatalysts confirming the presence of W  
14 in their surfaces. No N signal was detected confirming the absence of N-doping effect  
15 due to the  $\text{NH}_3$  used for the incorporation of W in composite catalysts. The surface  
16 content of W was calculated from peak areas and Wagner atomic sensitive factors [28].  
17 Results are summarized in **Table 1** where it can be noticed a lower W surface content  
18 for the NT- $\text{WO}_3$  catalyst that could be related to the higher porosity of the NT sample  
19 which can favour the incorporation of W in inner regions of the porous structure. On the  
20 other hand, **Fig.6 (e)** shows the high-resolution Ti 2p spectral region of P25- $\text{WO}_3$   
21 catalyst as an example. The binding energy of the Ti  $2p_{1/2}$  and Ti  $2p_{3/2}$  core levels at  
22  $464.7\text{ eV}$  and  $459.0\text{ eV}$ , respectively, together with their separation of  $5.7\text{ eV}$  confirm  
23 the valence state of Ti as  $\text{Ti}^{4+}$  in  $\text{TiO}_2$  [29,30]. **Fig.6 (f)** displays the high-resolution and  
24 peak-fitting results of W4f and Ti3p XPS spectra of P25- $\text{WO}_3$  catalyst as an example.  
25 Analysis of the W4f region is complicated due to the interference from the Ti3p level of  
26 the  $\text{TiO}_2$ . However, the position of the Ti3p peak can be fixed and its area calculated  
27 from the Ti2p peaks areas [28]. This makes possible to distinguish between the two  
28 signals (Ti3p and W4f) by deconvolution procedure, and to determine the valence of W  
29 from the position of the W4f level. The binding energy of the peaks located at  $37.8\text{ eV}$   
30 and  $35.7\text{ eV}$  corresponds to W  $4f_{5/2}$  and W  $4f_{7/2}$  components, respectively, and their  
31 area ratio of 3:4 confirm the presence of W as  $\text{W}^{6+}$  in  $\text{WO}_3$  [18,30]. Similar results were  
32 obtained for NT- $\text{WO}_3$  catalyst (not shown).

33 The UV-Vis diffuse reflectance spectra of the photocatalysts (**Fig.7**) showed a higher  
34 optical absorbance in the visible region above ca.  $400\text{ nm}$  for  $\text{TiO}_2$ - $\text{WO}_3$  catalysts due  
35 to the  $\text{WO}_3$  loading. The optical energy band gap ( $E_g$ ) was calculated by means of  
36 Tauc's expression and results are summarized in **Table 1** together with the wavelength  
37 of absorption edge. These values are approximate due to the need of extrapolation of  
38 the resulting curve (not shown). However a value of  $3.19\text{ eV}$  was calculated for P25  
39 catalyst similar to  $3.2\text{ eV}$  previously reported for bare  $\text{TiO}_2$  [11]. It is noticeable a  
40 decrease of band gap energy by coupling the  $\text{TiO}_2$  with  $\text{WO}_3$  from ca.  $3.2\text{ eV}$  to  $3.05\text{ eV}$   
41 and  $2.98\text{ eV}$  calculated for P25- $\text{WO}_3$  and NT- $\text{WO}_3$  catalysts, respectively, which is in  
42 agreement to previously reported values for similar materials [15]. These results  
43 indicate that both P25- $\text{WO}_3$  and NT- $\text{WO}_3$  can be promising photocatalysts to use  
44 visible light.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42

### 3.2. Visible light response of the photocatalysts

The effectiveness of the catalysts in the use of visible light was tested using IBP as target compound by cutting off all the wavelengths lower than 390 nm of the Xe lamp in the solar simulator. Results of photocatalytic depletion of IBP and its mineralization with all the catalysts synthesized are presented in **Fig.8**.

Regarding IBP depletion (**Fig.8 (a)**), once confirmed the absence of IBP degradation through direct photolysis as expected according to its absorption UV-Vis spectrum, it can be noticed the positive effect of WO<sub>3</sub> loading on the photocatalytic activity of TiO<sub>2</sub>-WO<sub>3</sub> photocatalysts under visible light irradiation compared to bare TiO<sub>2</sub>. In addition, it is noticeable the lowest IBP degradation rate with the sample NT-T, thus indicating that the heat-treatment and different structural properties of the calcined NT are not responsible of the high catalytic activity in the NT-WO<sub>3</sub> photocatalyst. Also once the N-doping effect has been ruled out, the enhancement observed in the photocatalytic activity of the WO<sub>3</sub> coupled materials can be related to the lowest band gap energy observed (**Table 1**) due to WO<sub>3</sub> presence, which makes them easily excited by the visible light [15]. In addition, the presence of WO<sub>3</sub> can promote the charge transfer between photogenerated electrons from the conduction band of TiO<sub>2</sub> to the WO<sub>3</sub> conduction band, accompanied by holes transfer from the valence band of WO<sub>3</sub> to the TiO<sub>2</sub> valence band. The charge separation mechanism has been previously reported [15,17,18,27], and provokes an increase in the lifetime of the photogenerated pair electron/hole avoiding its recombination to some extent. As a consequence of both, higher visible light absorption and lower recombination rate, the photonic efficiency (i.e. reacted molecules/incident photons) of the photocatalytic process is increased. The improvement of composite materials respect their corresponding TiO<sub>2</sub> was higher in NT-WO<sub>3</sub> photocatalyst than P25-WO<sub>3</sub>. Taking into account that NT-T sample led to a lower degradation rate than NT, the formation of elongated anatase particles from the titanate structures seems not to be the reason of this behaviour. Thus, it seems plausible that NT material presented a better distribution and higher dispersion of WO<sub>3</sub> particles since also offered a developed porous structure and higher surface area than P25 together with a large ion-exchange capacity [19,20]. This hypothetic higher dispersion together with the slightly higher amount of WO<sub>3</sub> in NT-WO<sub>3</sub> (**Table 1**) could be the reasons of the higher visible light absorption capacity involving the largest improvement in NT-WO<sub>3</sub> photocatalytic activity compared to P25-WO<sub>3</sub>, although additional characterization analysis confirming this hypothesis would be needed.

Regarding TOC evolution (**Fig.8 (b)**) it is noticeable the fastest mineralization rate observed with the NT-WO<sub>3</sub> photocatalyst reaching 40% TOC removal in 2 h whereas P25-WO<sub>3</sub> did not show a significant mineralization degree. These and previous results point out the higher photocatalytic activity of NT-WO<sub>3</sub> photocatalyst under visible light radiation.



### 3.3. Photocatalytic degradation of ECs in MWW

The effectiveness of the photocatalysts in a more realistic application was studied using a MWW effluent as aqueous matrix spiked with IBP, MTP and CAF. The average values of the main MWW secondary effluent parameters are summarized in **Table 2**. It can be highlighted the amount of carbonate/bicarbonate as inorganic carbon (IC) that was not removed prior to use and their buffer role maintaining the pH of the reaction medium around pH=8.3.

Regarding the process applied, **Table 3** summarizes the main results of ECs removal at 120 min upon the treatments tested, together with **Fig.9** and **Fig.10** that show the time-evolution of ECs and TOC respectively, only for NT-WO<sub>3</sub> catalyst as an example. It can be noticed that direct photolysis exerts no effect on the case of IBP removal and only 5 and 7% removal was observed for CAF and MTP, respectively. The time-evolution of ECs concentration during photolysis is also shown in **Fig.9**. Although these compounds do not absorb radiation in the wavelength range used in this work, MWW content could provoke indirect photolysis reactions [31,32]. The insignificant evolution of mineralization during photolysis can be observed in **Fig.10** and the low value of final TOC removal is also presented in **Table 4**. Taking into account that the contribution of the initial concentration of ECs to the initial TOC content is around 10% (3.7 mgL<sup>-1</sup>), the mineralization observed would be mainly associated to the MWW TOC content.

Regarding the adsorption capacity of the catalysts, none of them gave place to ECs removal higher than 10% (**Table 3**). It is noticeable that no significant changes are observed in terms of ECs adsorption either due to W incorporation or textural properties modification in NT series, although the modification of adsorption capacity of these materials has been reported elsewhere [18]. However, a different behaviour is observed for the organic matter content of the MWW as the adsorption capacity of the catalysts is increased around 15% in both series, P25 and NT, after W incorporation (see values in **Table 4**). Also it is noticeable a somewhat higher adsorption capacity in NT series respect to P25 due to its more developed porous structure. The fact that NT series, in which a significant decrease in textural parameters was observed after calcination, presented the same increase in adsorption capacity than P25 series points out that this phenomenon is mainly related to the W species in the catalysts surface. In fact, it has been reported that the presence of a monolayer of WO<sub>x</sub> species on TiO<sub>2</sub> can significantly increase the surface acidity leading to the fact that composite materials TiO<sub>2</sub>-WO<sub>3</sub> can adsorb more organic reactants [18,33].

For photocatalytic oxidation process with P25 series, as shown in **Table 3**, the incorporation of W did not give place to higher ECs removal, leading around 75, 80 and 90% for IBP, CAF and MTP, respectively, with both P25 and P25-WO<sub>3</sub> catalysts. In spite of the improvement observed by introducing W when irradiated with visible light, bare P25 presents a higher catalytic activity under UVA radiation and thus, when used the entire simulated solar light spectrum (320-800 nm), the beneficial effect of W is not noticeable. Similar results were observed in terms of mineralization (evolution not shown, final value given in **Table 4**). On the contrary, NT photocatalyst showed the poorest behaviour during the reaction but a significant increase in the photocatalytic

1 activity of NT-WO<sub>3</sub> respect to NT precursor was noticed. Thus, in this case, ECs  
2 conversions around 70, 80 and 90% for IBP, CAF and MTP, respectively, similar to  
3 those reached in P25 series were achieved. In addition, the order of reactivity during  
4 photocatalytic oxidation regardless of the catalyst used was MTP>CAF>IBP in contrast  
5 to the rate constants of the direct reaction of these ECs and hydroxyl radicals, HO<sup>•</sup>,  
6 ( $k_{OH-IBP}=7.4 \times 10^9 \text{ M}^{-1}\text{s}^{-1}$  [34],  $k_{OH-CAF}=5.9 \times 10^9 \text{ M}^{-1}\text{s}^{-1}$  [35],  $k_{OH-MTP}=2.1 \times 10^9 \text{ M}^{-1}\text{s}^{-1}$  [36]).  
7 This may be an indication that not only HO<sup>•</sup> attack is responsible of ECs removal but  
8 also different ways such as direct  $h^+$  oxidation can be taking place.

9 All the ozone treatments led to complete ECs depletion in less than 45 min of reaction  
10 time (conversion higher than 99.9%) regardless of the presence/absence of catalysts  
11 and/or radiation in contrast to photocatalytic oxidation. Both direct and indirect ozone  
12 reactions may take place according to the pH=8.3 of the reaction medium that was kept  
13 constant throughout the reaction time due to the buffer character of the MWW. On the  
14 other hand, slight differences can be noticed among ozone processes with a different  
15 behaviour mainly depending on the rate constant of the direct ozone-EC reaction ( $k_{O_3-}$   
16  $IBP=9.1 \text{ M}^{-1}\text{s}^{-1}$  [37],  $k_{O_3-CAF}=6.5 \times 10^2 \text{ M}^{-1}\text{s}^{-1}$  [35],  $k_{O_3-MTP}=6.2 \times 10^3 \text{ M}^{-1}\text{s}^{-1}$  (pH=8) [38]).  
17 Although photocatalytic ozonation gave place to a faster depletion rate, it is noticeable  
18 in **Fig.9** that the differences between ozone processes are only significant for IBP  
19 which presented the lowest rate constant of direct ozone reaction, being practically  
20 negligible in the case of CAF and MTP. Main differences between ozone and O<sub>3</sub>-  
21 catalytic processes were obtained in terms of TOC removal as shown in **Table 4** and  
22 **Fig.10**. Ozone alone led to 31% mineralization produced mainly during the first minutes  
23 of reaction time and then stopped likely due to the formation of refractory compounds  
24 to ozone attack. Production of HO<sup>•</sup>, main responsible species for mineralization, seems  
25 to be insufficient at pH=8.3 in the ozonation process. The degree of mineralization is  
26 decreased in the presence of P25. This material does not have any positive effect in  
27 catalytic ozonation leading to even lower mineralization than ozone alone probably due  
28 to an inefficient consumption of O<sub>3</sub> onto the catalyst surface. In contrast, NT slightly  
29 increased TOC removal up to 39% that can be associated to the higher adsorption  
30 capacity of this material since mineralization rate is similar to ozone process (not  
31 shown). On the other hand, W containing photocatalysts, P25-WO<sub>3</sub> and NT-WO<sub>3</sub>, led to  
32 higher mineralization around 47%, with also higher TOC removal rate than ozone alone  
33 (see **Fig.10** for NT-WO<sub>3</sub>), thus indicating a catalytic effect to some extent. This  
34 improvement can be related to (1) the catalytic effect of WO<sub>3</sub> and/or (2) the higher  
35 adsorption capacity of TiO<sub>2</sub>-WO<sub>3</sub> catalysts. The catalytic activity of WO<sub>3</sub> in aqueous  
36 ozone decomposition or catalytic ozonation has not been extensively reported,  
37 however some evidences have been found. Nishimoto et al. observed a higher TOC  
38 removal during phenol ozonation with WO<sub>3</sub> suggesting that it functions as an ozonation  
39 catalyst in a similar manner to MnO<sub>2</sub> or TiO<sub>2</sub> [39]. In addition, WO<sub>3</sub> has been widely  
40 used as the active component of O<sub>3</sub> gas sensors, in which O<sub>3</sub> undergoes dissociative  
41 adsorption onto the WO<sub>3</sub> surface [40,41]. On the other hand, another plausible  
42 explanation of the catalytic activity of TiO<sub>2</sub>-WO<sub>3</sub> catalysts during ozonation compared to  
43 bare TiO<sub>2</sub> is the enhanced adsorption capacity due to the presence of WO<sub>3</sub> [18,33].  
44 Thus, TiO<sub>2</sub> has been widely used as catalyst for ozonation processes and proposed  
45 mechanisms involve surface reactions between adsorbed O<sub>3</sub> and organic compounds

1 [42]. The fact that bare TiO<sub>2</sub> samples studied here do not show any catalytic activity in  
2 the process could be related to an inefficient decomposition of O<sub>3</sub> due to the lack of  
3 organic matter near the catalyst surface. However, the enhanced adsorption capacity  
4 of TiO<sub>2</sub>-WO<sub>3</sub> catalysts can lead to an increase in the local concentration of organic  
5 matter in the vicinity of their surface [18], thus allowing surface reactions between  
6 adsorbed O<sub>3</sub>-organic compounds. Both hypotheses should be considered but some  
7 additional work to clarify the prevailing mechanism is needed. Finally, the highest  
8 mineralization degree was obtained with the photocatalytic ozonation process  
9 regardless of the catalyst used. This is in agreement with the expected synergistic  
10 effect between ozone and irradiated semiconductors. This synergistic effect is due to  
11 the reaction of O<sub>3</sub> with conduction band electrons of TiO<sub>2</sub> and WO<sub>3</sub>, or with the  
12 superoxide ion radical generated (O<sub>2</sub><sup>•-</sup>), in both cases leading to the formation of higher  
13 concentrations of hydroxyl radicals (HO<sup>•</sup>), main responsible of mineralization [5,8,39].

14 On the other hand, MWW parameters after the most representative treatments with  
15 NT-WO<sub>3</sub> catalyst are summarized in **Table 2**. As commented above, photocatalytic  
16 ozonation gave place to higher TOC depletion than individual treatments. Similar  
17 trends are observed both for COD and aromaticity, reaching a 66% COD reduction in  
18 the combined treatment compared with 10% in photocatalytic oxidation and 19% upon  
19 single ozonation. Also the effectiveness of catalytic ozonation can be observed in terms  
20 of TOC, COD and aromaticity. In addition, it can be noticed that the pH remain  
21 unalterable after the treatments applied as a consequence of the buffer effect of the IC  
22 content (from carbonate/bicarbonate) also unalterable upon the treatments.

23 The comparison of the catalysts in the photocatalytic ozonation process is shown with  
24 more detail in **Fig.11** and **Fig.12** which depict ECs concentration and TOC with time,  
25 respectively. Again it can be noticed that ozone alone is able to completely remove the  
26 ECs in a short time. Main differences between ozonation and photocatalytic ozonation  
27 were only observed in IBP and CAF depletion according to their lower rate constant of  
28 the direct ozone reaction. In these cases, indirect and photocatalytic contributions are  
29 more important than for MTP. It can be also noticed the highest catalytic activity of WO<sub>3</sub>  
30 composite materials compared to TiO<sub>2</sub> precursors although main differences were  
31 observed in TOC evolution (**Fig.12**). In addition to the differences in the adsorption  
32 capacity, the highest mineralization rate was observed for the TiO<sub>2</sub>-WO<sub>3</sub> catalysts.  
33 These catalysts take the advantage of using a greater fraction of solar light radiation in  
34 the visible region due to the presence of WO<sub>3</sub> as demonstrated in section 3.2, but also  
35 a significant contribution of dark catalytic ozone reactions. The best performance was  
36 attained with NT-WO<sub>3</sub> photocatalyst which leads to 64% TOC removal. The  
37 improvement observed in the NT series after introducing the WO<sub>3</sub> is remarkably higher  
38 than in the P25 series in good agreement with visible light response results probably  
39 due to a better dispersion of WO<sub>3</sub>. To elucidate the reaction mechanism of  
40 photocatalytic ozonation using NT-WO<sub>3</sub> catalyst it is necessary to consider the different  
41 processes involved and will be the subject of future work.

42

43

#### 1 **4. Conclusions**

2 TiO<sub>2</sub>-WO<sub>3</sub> composite catalysts have been synthesized with around 4% of WO<sub>3</sub> and  
3 visible light response, and successfully applied for the removal of emerging  
4 contaminants in urban wastewater and mineralization of the effluent through  
5 photocatalytic ozonation. Ozone alone is able to completely remove the emerging  
6 contaminants in the wastewater matrix but the mineralization degree reached is  
7 relatively low. Photocatalytic ozonation gives place to the highest mineralization rate  
8 regardless of the catalyst used. Titanate nanotubes structure is not efficient in the  
9 photocatalytic oxidation and photocatalytic ozonation processes, but it is a good  
10 precursor of composite catalysts due to its textural and surface properties. Titanate  
11 nanotubes gave place to a composite catalyst NT-WO<sub>3</sub> with elongated anatase  
12 particles, a well-developed porous structure and high dispersion of WO<sub>x</sub> species  
13 showing visible light absorption capacity. The best performance of the NT-WO<sub>3</sub> catalyst  
14 compared to bare TiO<sub>2</sub> is related to several mixed contributions such as use of a  
15 greater fraction of solar light radiation, higher organic compounds adsorption capacity  
16 and catalytic activity in ozone reactions. The contribution of the different phenomena to  
17 elucidate the reaction mechanism with this catalyst will be the subject of future work.

18

#### 19 **Acknowledgements**

20 This work has been supported by the Spanish Ministerio de Economía y  
21 Competitividad (MINECO) and European Feder Funds through the project CTQ2012-  
22 35789-C02-01. Authors acknowledge the SACSS-SAIUEX and UAI-ICP for the  
23 characterization analyses. A. Rey thanks the University of Extremadura for a  
24 postdoctoral research contract. M.D. Hernández-Alonso thanks MINECO for the award  
25 of her postdoctoral contract from the "Ramón y Cajal" program. E. Mena thanks the  
26 Consejería de Empleo, Empresa e Innovación (Gobierno de Extremadura) and  
27 European Social Fund for providing her a predoctoral FPI grant (Ref. PD12059).

28

#### 29 **References**

---

[1] J.L. Santos, I. Aparicio, M. Callejón, E. Alonso, J. Hazard. Mater. 164 (2009) 1509-1516.

[2] D. Barceló, M. Petrovic (Eds.), Emerging contaminants from industrial and municipal wastes. Occurrence, analysis and effects. The Handbook of Environmental Chemistry 5-S1. Springer, Berlin, 2008.

[3] B. Halling-Sorensen, S. Nors-Nielsen, P.F. Lanzky, F. Ingerslev, H.C. Holten Lützhof, S.E. Jorgensen, Chemosphere 36 (1998) 357-393.

[4] S. Esplugas, D.M. Bila, L.G.T. Krause, M. Dezotti, J. Hazard. Mater. 149 (2007) 631-642.

- 
- [5] T.E. Agustina, H.M. Ang, V.K. Vareek, J. Photochem. Photobiol. C: Photochem. Rev. 6 (2005) 264-273.
- [6] E.M. Rodríguez, G. Fernández, P.M. Alvarez, F.J. Beltrán, Water Res. 46 (2012) 152-166.
- [7] F.J. Rivas, F.J. Beltrán, A. Encinas, J. Environ. Manage. 100 (2012) 10-15.
- [8] E. Mena, A. Rey, B. Acedo, F.J. Beltrán, S. Malato, Chem. Eng. J. 204-206 (2012) 131-140.
- [9] M.D. Hernández-Alonso, J.M. Coronado, A.J. Maira, J. Soria, V. Loddo, V. Augugliaro. Appl. Catal. B: Environ. 39 (2002) 257-267.
- [10] S. Malato, P. Fernández-Ibáñez, M. I. Maldonado, J. Blanco, W. Gernjak, *Catal. Today* 147 (2009) 1-59.
- [11] M.D. Hernández-Alonso, F. Fresno, S. Suárez, J.M. Coronado, Energy Environ. Sci. 2 (2009) 1231-1257.
- [12] C. Shifu, C. Lei, G. Shen, C. Gengyu, Powder Technol. 160 (2005) 198-202.
- [13] Y.T. Kwon, K. Y. Song, W.I. Lee, G. J. Choi, Y.R. Do, J. Catal. 191 (2000) 192-199.
- [14] B. Tryba, M. Piszcz, A.W. Morawski, Int. J. Photoenergy (2009) (Article ID 297319) 1-7.
- [15] M. Ismail, L. Boussemi, O. Zahraa, J. Photochem. Photobiol. A: Chem. 222 (2011) 314-322.
- [16] M. Xiao, L. Wang, X. Huang, Y. Wu, Z. Dang, J. Alloys Compd. 470 (2009) 486-491.
- [17] V. Iliev, D. Tomova, S. Rakovsky, A. Eliyas, G. Li Puma, J. Mol. Catal. A: Chem. 327 (2010) 51-57.
- [18] D. Tomova, V. Iliev, S. Rakovsky, M. Anachkov, A. Eliyas, G. Li Puma, J. Photochem. Photobiol. A: Chem. 231 (2012) 1-8.
- [19] M.D. Hernández-Alonso, S. García-Rodríguez, B. Sánchez, J.M. Coronado. Nanoscale 3 (2011) 2233-2240.
- [20] M.D. Hernández-Alonso, S. García-Rodríguez, S. Suárez, R. Portela, B. Sánchez, J.M. Coronado, Appl. Catal. B: Environ. 110 (2011) 251-259.
- [21] H. Bader, J. Hoigné, Water Res. 15 (1981) 449-456.
- [22] K.S.W. Sing, D.H. Everett, R.A.W. Haul, L. Moscou, R.A. Pierotti, J. Rouquerol, T. Siemieniowska, Pure Appl. Chem. 57 (1985) 603-619.

- 
- [23] J. Yan, G. Wu, N. Guan, L. Li, Z. Li, X. Cao, *Phys. Chem. Chem. Phys.* 15 (2013) 10978-10988.
- [24] I.M. Arabatzis, S. Antonaraki, T. Stergiopoulos, A. Hiskia, E. Papaconstantinou, M.C. Bernard, P. Falaras, *J. Photochem. Photobiol. A: Chem.* 149 (2002) 237-245.
- [25] M.A. Vuurman, I.E. Wachs, A.M. Hirt, *J. Phys. Chem.* 95 (1991) 9928-9937.
- [26] C. Sanato, M. Odziemkowski, M. Ulmann, J. Augustynski, *J. Am. Chem. Soc.* 123 (2001) 10639-10649.
- [27] K.K. Akurati, A. Vital, J.P. Delleman, K. Michalow, T. Graule, D. Ferri, A. Baiker, *Appl. Catal. B: Environ.* 79 (2008) 53-62.
- [28] C.D. Wagner, L.E. Davis, M.V. Zeller, J.A. Taylor, R.H. Raymond, L.H. Gale, *Surf. Interface. Anal.* 3 (1981) 211-225.
- [29] M.W. Xiao, L. Wang, X.J. Huang, Y.D. Wu, Z. Dang, *J. Alloys Compd.* 470 (2009) 486-491.
- [30] Y. Li, L. Chen, Y. Guo, X. Sun, Y. Wei, *Chem. Eng. J.* 181-182 (2012) 734-739.
- [31] C.C. Ryan, D.T. Tan, W.A. Arnold, *Water Res.* 45 (2011) 1280-1286.
- [32] L.E. Jacobs, L.K. Weavers, E.F. Houtz, Y.P. Chin, *Chemosphere* 86 (2012) 124-129.
- [33] Y.T. Kwon, K.Y. Song, W.I. Lee, G.J. Choi, Y.R. Do, *J. Catal.* 191 (2000) 192-199.
- [34] M.M. Huber, S. Canonica, G.Y. Park, U. Von Gunten, *Environ. Sci. Technol.* 37 (2003) 1016-1024.
- [35] R. Broséus, S. Vincent, K. Aboulfadl, A. Daneshvar, S. Sauvé, B. Barbeau, M. Prévost, *Water Res.* 43 (2009) 4707-4717.
- [36] I. Sires, N. Oturan, M.A. Oturan, *Water Res.* 44 (2010) 3109-3120.
- [37] M.M. Huber, A. Gobel, A. Joss, N. Hermann, D. Loffler, C. McArdell, A. Ried, H. Siegrist, T.A. Ternes, U. Von Gunten, *Environ. Sci. Technol.* 39 (2005) 4290-4299.
- [38] F.J. Benítez, J.L. Acero, F.J. Real, G. Roldán, *Chemosphere* 77 (2009) 53-59.
- [39] S. Nishimoto, T. Mano, Y. Kameshima, M. Miyake, *Chem. Phys. Lett.* 500 (2010) 86-89.
- [40] J. Guerin, K. Aguir, M. Bendahan. *Sensor. Actuat. B: Chem.* 119 (2006) 327-334.
- [41] V. Oison, L. Saadi, C. Lambert-Mauriat, R. Hayn. *Sensor. Actuat. B: Chem.* 160 (2011) 505-510.
- [42] B. Kasprzyk-Hordern, M. Ziólek, J. Nawrocki, *Appl. Catal. B: Environ.* 46 (2003) 639-669.

---

## Figure Captions

**Fig.1.** Scheme of the experimental set-up

**Fig.2.** N<sub>2</sub> adsorption-desorption isotherms of the catalysts

**Fig.3.** XRD patterns of the catalysts. Crystalline phases detected: anatase (A), rutile (R)

**Fig.4.** TEM images of the catalysts

**Fig.5.** Raman spectra of P25-WO<sub>3</sub> and NT-WO<sub>3</sub> photocatalysts

**Fig.6.** XPS full spectra of the catalysts (a, b, c and d). High-resolution XPS spectra of Ti2p (e) and Ti3p/W4f (f) spectral regions of P25-WO<sub>3</sub> catalyst.

**Fig.7.** DR UV–Vis spectra of the catalysts

**Fig.8.** Time evolution of IBP dimensionless concentration (a) and dimensionless TOC (b) during photocatalytic oxidation under visible light radiation ( $\lambda=390-800$  nm)

**Fig.9.** Time evolution of ECs dimensionless concentration during all the treatments applied with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and NT-WO<sub>3</sub> catalyst

**Fig.10.** Time evolution of TOC dimensionless concentration during all the treatments applied with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and NT-WO<sub>3</sub> catalyst

**Fig.11.** Time evolution of ECs dimensionless concentration during ozonation and photocatalytic ozonation with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and all the catalysts studied

**Fig.12.** Time evolution of TOC dimensionless concentration during ozonation and photocatalytic ozonation with MWW effluent as aqueous matrix under simulated solar light radiation ( $\lambda=320-800$  nm) and all the catalysts studied

## Table Captions

**Table 1.** Properties of the catalysts

**Table 2.** Characterization of MWW effluent before and after some treatments with NT-WO<sub>3</sub> catalyst (t=120 min)

**Table 3.** ECs removal (%) after 120 min reaction upon the different treatments applied

**Table 4.** TOC removal (%) after 120 min reaction upon the different treatments applied

**Table 1.** Properties of the catalysts

| CATALYST            | WO <sub>3</sub><br>(wt. %) | S <sub>BET</sub><br>(m <sup>2</sup> g <sup>-1</sup> ) | V <sub>PORE</sub><br>(cm <sup>3</sup> g <sup>-1</sup> ) | W <sub>XPS</sub><br>(at. %) | E <sub>g</sub><br>(eV) | λ<br>(nm) |
|---------------------|----------------------------|---|---|-----------------------------|------------------------|-----------|
| P25                 | ---                        | 52  | 0.25  | ---                         | 3.19                   | 389       |
| P25-WO <sub>3</sub> | 4.1                        | 49  | 0.28  | 1.6                         | 3.05                   | 407       |
| NT                  | ---                        | 320   | 1.39  | ---                         | 3.18                   | 390       |
| NT-WO <sub>3</sub>  | 4.5                        | 195   | 1.17  | 0.9                         | 2.98                   | 416       |
| NT-T                | ---                        | 208   | 1.19  | ---                         | ---                    | ---       |

**Table 2.** Characterization of MWW effluent before and after some treatments with NT-WO<sub>3</sub> catalyst (t=120 min)

| PARAMETER  | Before<br>treatment* | Photocatalytic<br>oxidation | Ozonation | Catalytic<br>ozonation | Photocatalytic<br>ozonation |
|--|----------------------|-----------------------------|-----------|------------------------|-----------------------------|
| TOC (mgC L <sup>-1</sup> )                           | 35.3                 | 22.8                        | 26.9      | 20.2                   | 12.8                        |
| IC (mgC L <sup>-1</sup> )                            | 42.0                 | 40.1                        | 38.3      | 41.5                   | 36.4                        |
| pH   | 8.31                 | 8.34                        | 8.29      | 8.28                   | 8.33                        |
| Absorbance 254 nm                                    | 0.253                | 0.164                       | 0.116     | 0.058                  | 0.017                       |
| COD (mgO <sub>2</sub> L <sup>-1</sup> )              | 51                   | 46                          | 41        | 33                     | 17                          |
| BOD <sub>5</sub> (mgO <sub>2</sub> L <sup>-1</sup> ) | 32                   | n.m                         | n.m       | n.m                    | n.m                         |
| Phosphate (mg L <sup>-1</sup> )                      | 4                    | n.m                         | n.m       | n.m                    | n.m                         |

\*Average values between all batches




**Table 3.** ECs removal (%) after 120 min reaction upon the different treatments applied


| TREATMENT  | EC  | No catalyst                |                     |    |                    |
|--|-----|----------------------------|---------------------|----|--------------------|
| Photolysis   | IBP | 0                          |                     |    |                    |
|  | CAF | 5                          |                     |    |                    |
|  | MTP | 7                          |                     |    |                    |
| TREATMENT  | EC  | P25                        | P25-WO <sub>3</sub> | NT | NT-WO <sub>3</sub> |
| Adsorption   | IBP | 7                          | 8                   | 10 | 7                  |
|  | CAF | 8                          | 7                   | 4  | 6                  |
|  | MTP | 6                          | 8                   | 8  | 6                  |
| Photocatalysis   | IBP | 73                         | 76                  | 28 | 70                 |
|  | CAF | 77                         | 79                  | 31 | 82                 |
|  | MTP | 92                         | 90                  | 61 | 91                 |
| TREATMENT  | EC  | No catalysts/All catalysts |                     |    |                    |
| Ozonation<br>Catalytic ozonation<br>Photocatalytic ozonation | IBP |                            |                     |    |                    |
|  | CAF | >99.9                      |                     |    |                    |
|  | MTP |                            |                     |    |                    |

**Table 4.** TOC removal (%) after 120 min reaction upon the different treatments applied


| TREATMENT                | No catalysts |                     |    |                    |
|--------------------------|--------------|---------------------|----|--------------------|
| Photolysis               | 4            |                     |    |                    |
| Ozonation                | 31           |                     |    |                    |
| TREATMENT                | P25          | P25-WO <sub>3</sub> | NT | NT-WO <sub>3</sub> |
| Adsorption               | 3            | 17                  | 9  | 23                 |
| Photocatalysis           | 37           | 42                  | 31 | 37                 |
| Catalytic ozonation      | 23           | 48                  | 39 | 47                 |
| Photocatalytic ozonation | 47           | 55                  | 42 | 64                 |

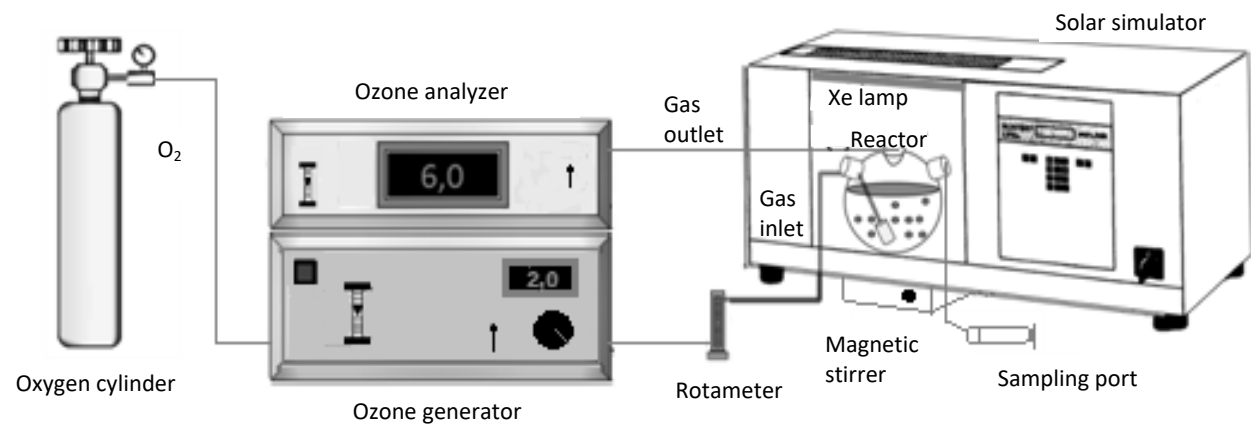


**Fig.1.** Scheme of the experimental set-up

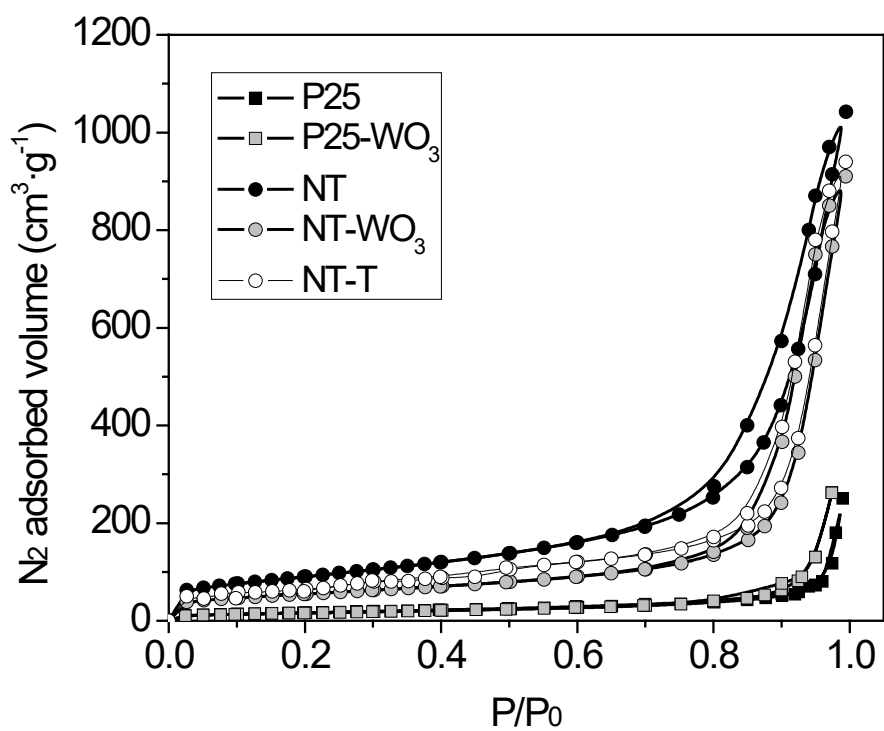


**Fig.2.**  $\text{N}_2$  adsorption-desorption isotherms of the catalysts

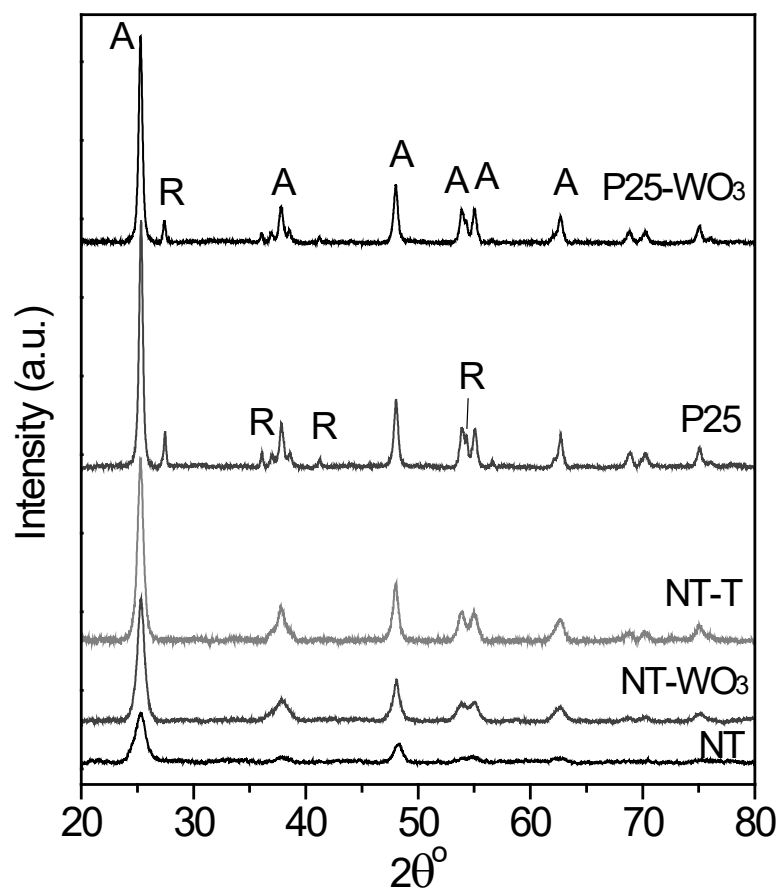


**Fig.3.** XRD patterns of the catalysts. Crystalline phases detected: anatase (A), rutile (R)

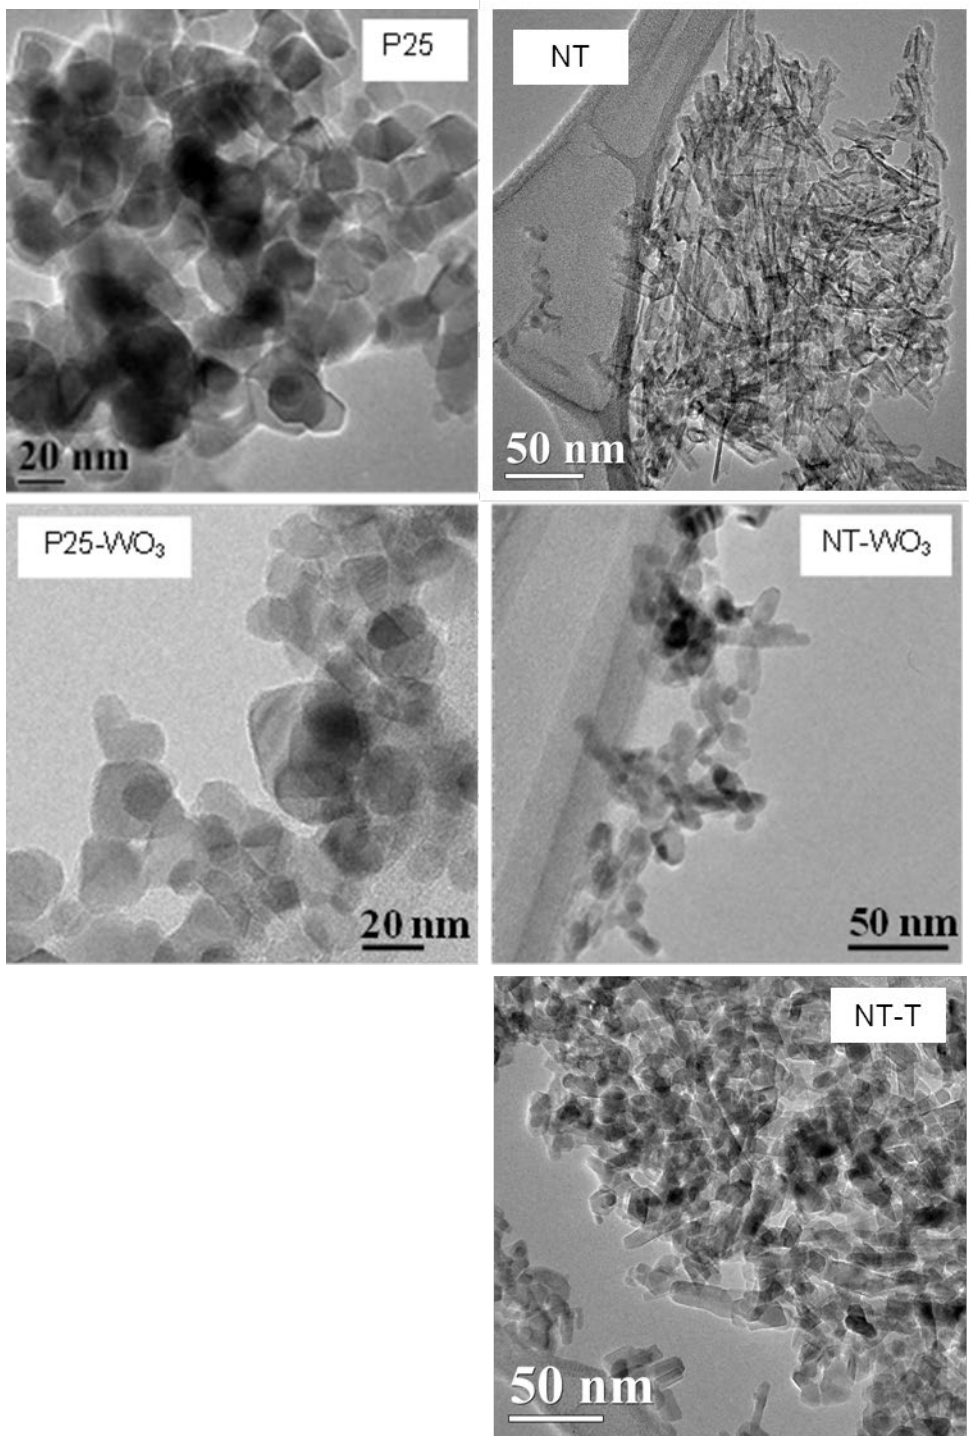


**Fig.4.** TEM images of the catalysts

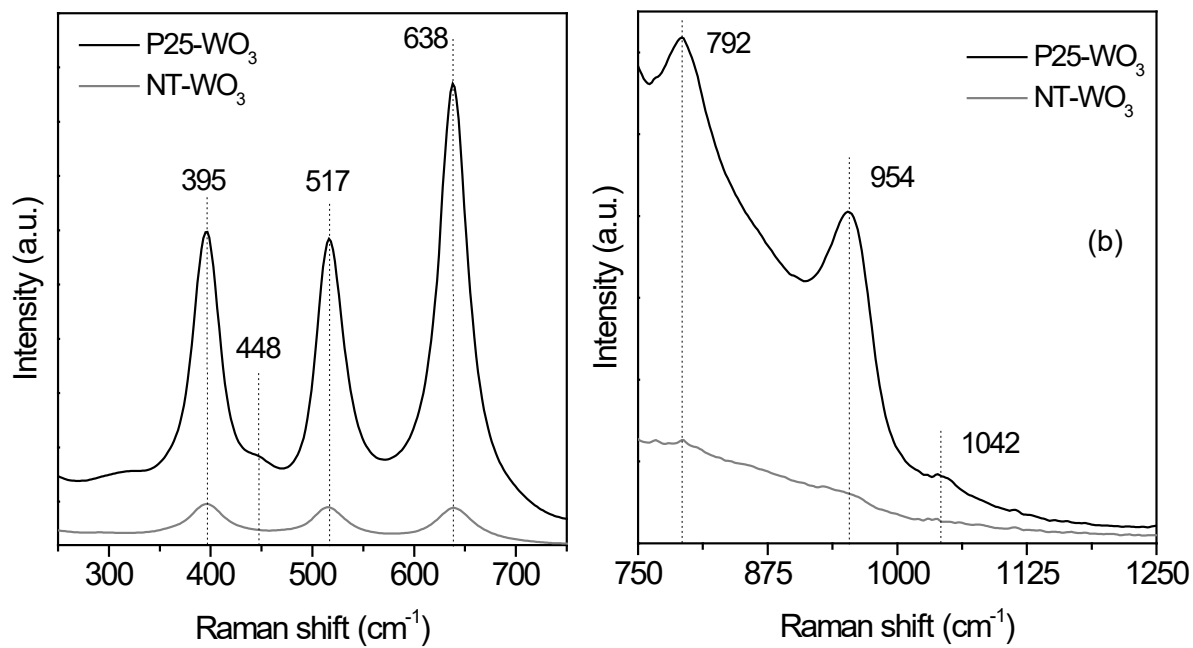

**Fig.5.** Raman spectra of P25-WO<sub>3</sub> and NT-WO<sub>3</sub> photocatalysts

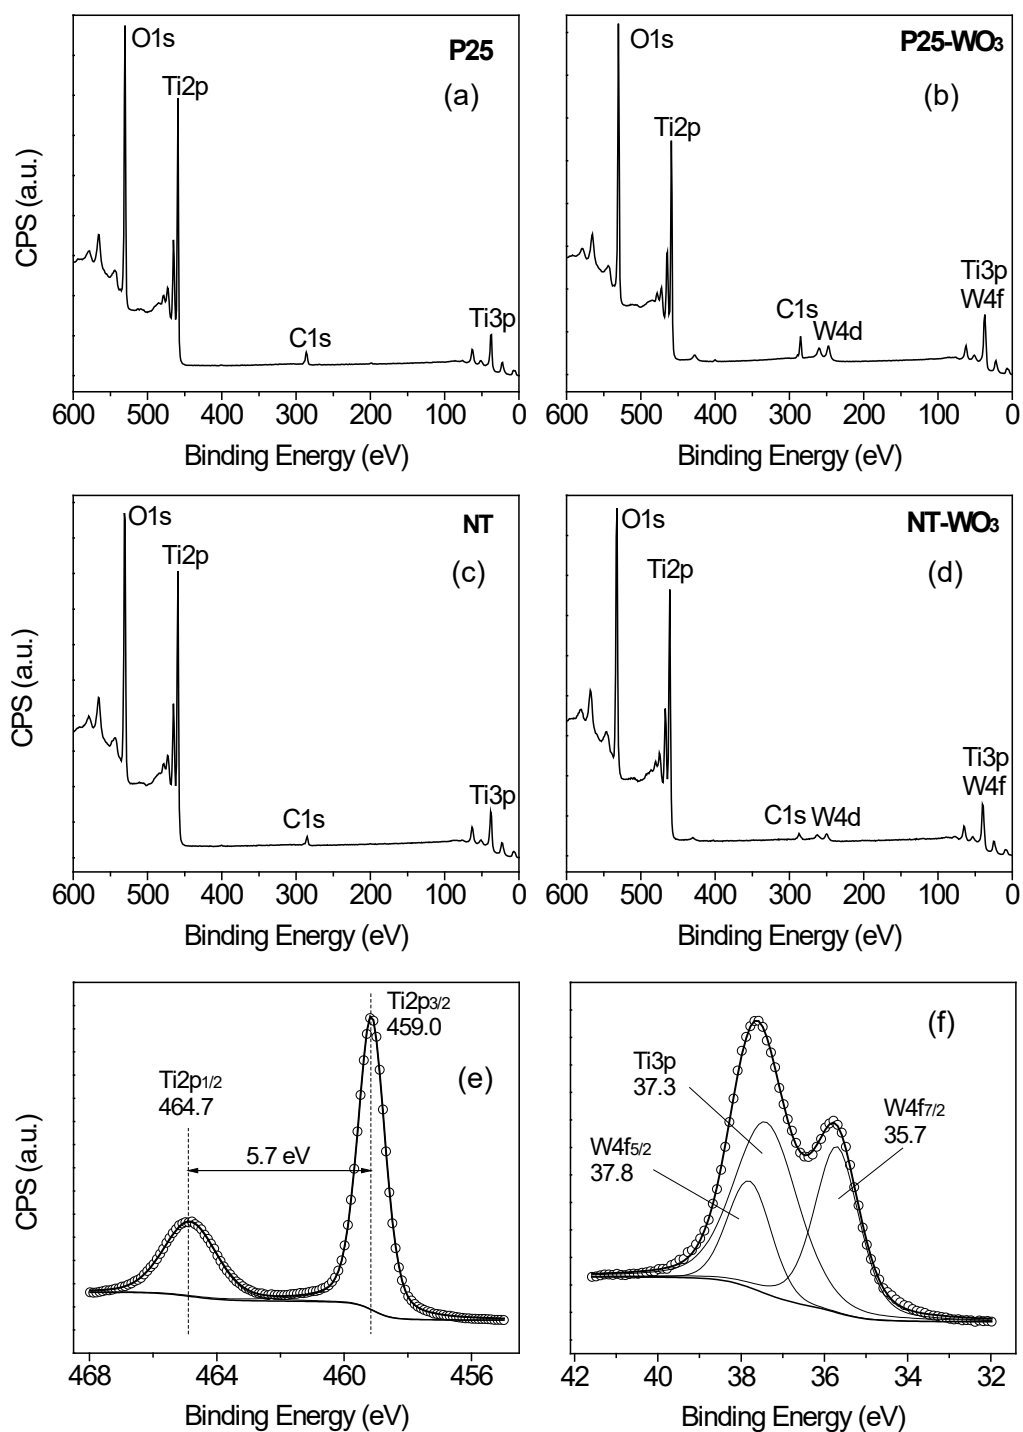


**Fig.6.** XPS full spectra of the catalysts (a, b, c and d). High-resolution XPS spectra of Ti2p (e) and Ti3p/W4f (f) spectral regions of P25-WO<sub>3</sub> catalyst.

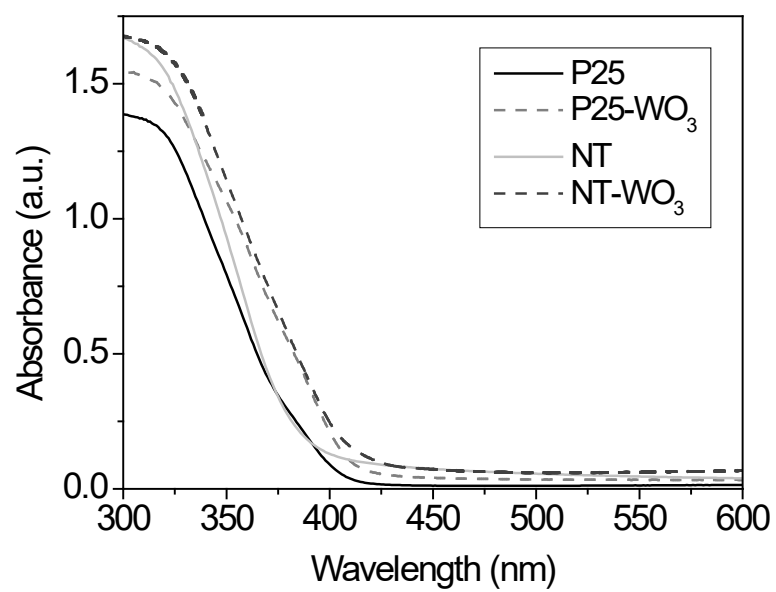


**Fig.7.** DR UV-Vis spectra of the catalysts




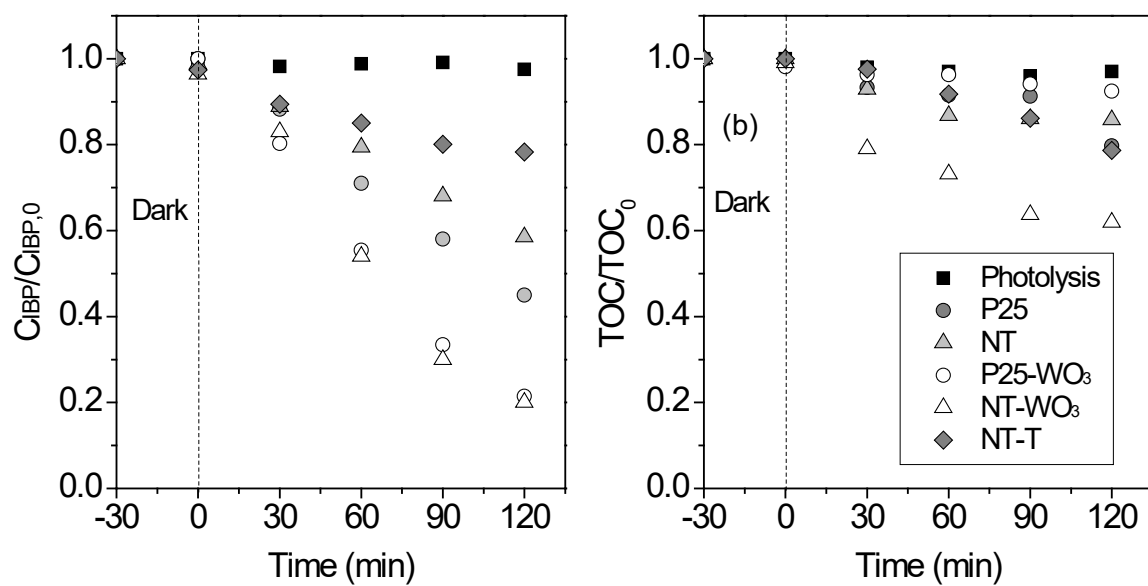




**Fig.8.** Time evolution of IBP dimensionless concentration (a) and dimensionless TOC (b) during photocatalytic oxidation under visible light radiation ( $\lambda=390-800$  nm)

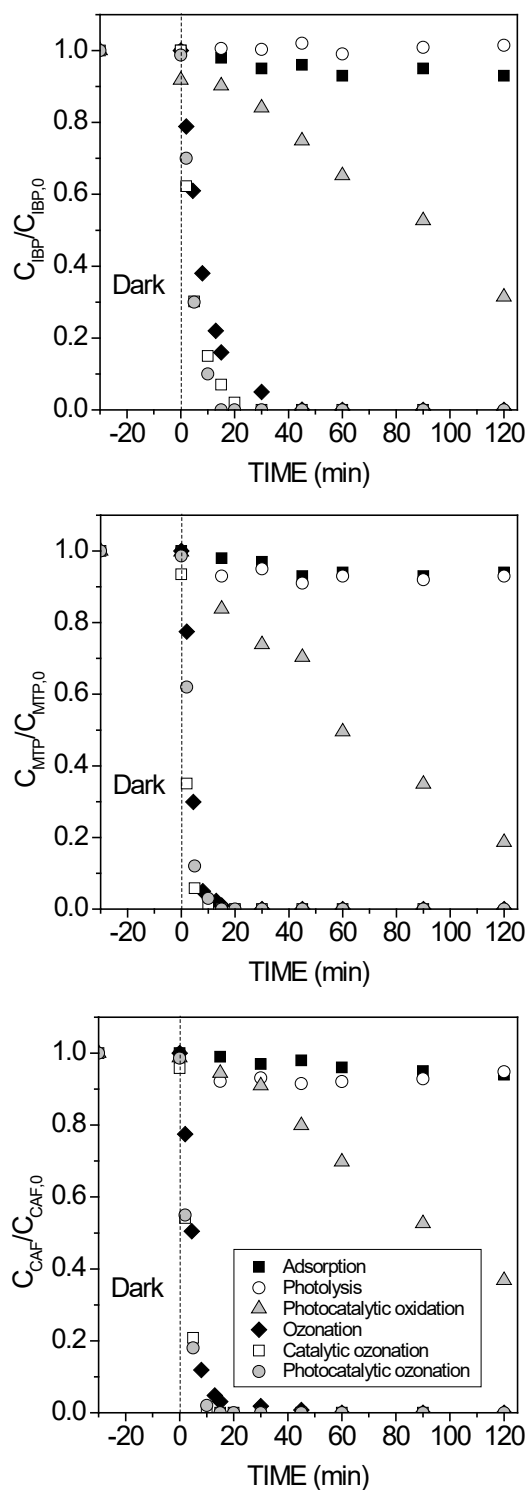


**Fig.9.** Time evolution of ECs dimensionless concentration during all the treatments applied with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and NT- $WO_3$  catalyst

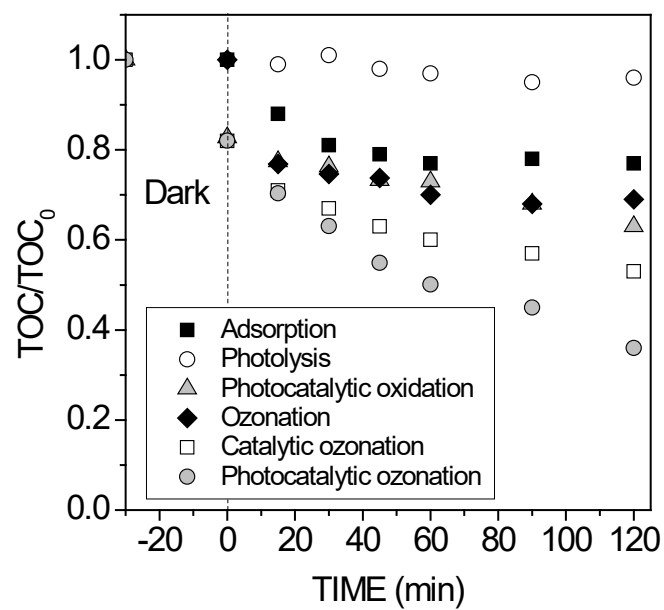

**Fig.10.** Time evolution of TOC dimensionless concentration during all the treatments applied with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and NT-WO<sub>3</sub> catalyst

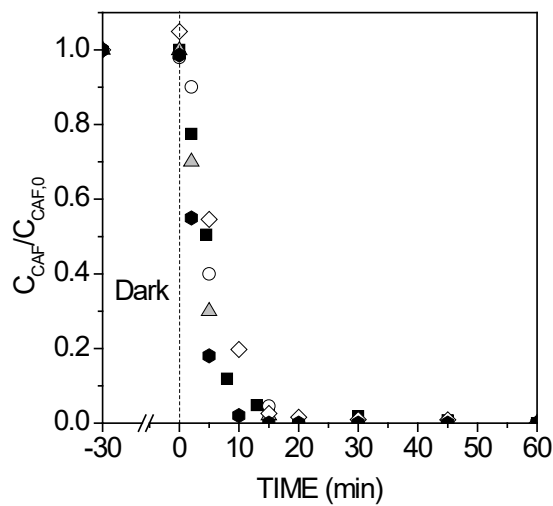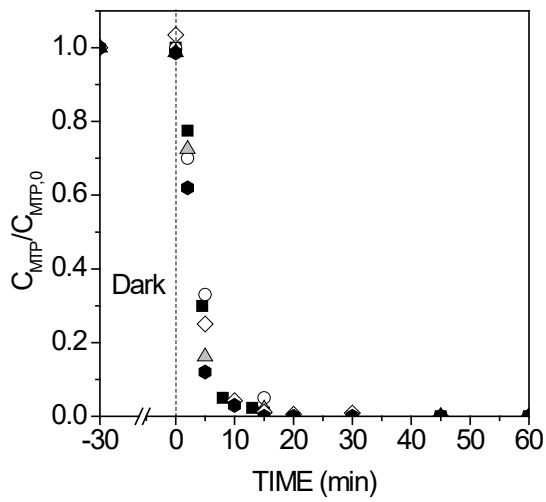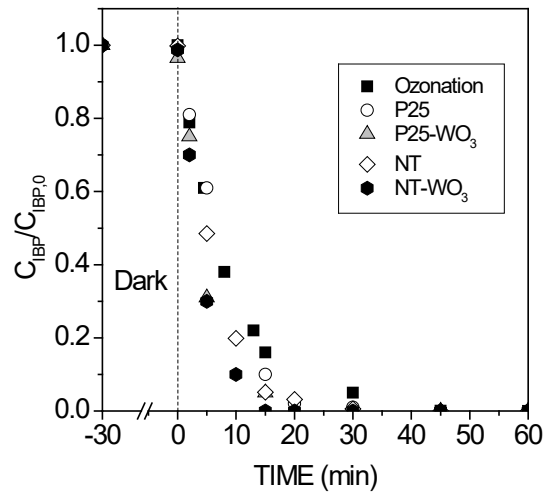

**Fig.11.** Time evolution of ECs dimensionless concentration during ozonation and photocatalytic ozonation with aqueous matrix MWW effluent under simulated solar light radiation ( $\lambda=320-800$  nm) and all the catalysts studied

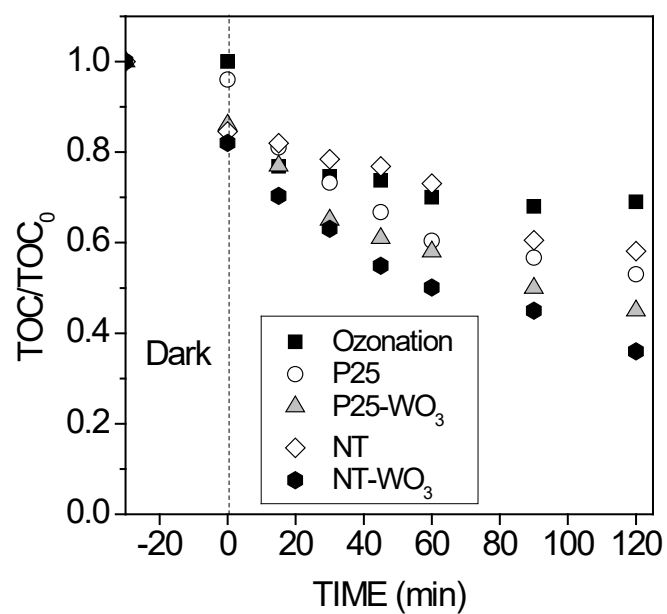

**Fig.12.** Time evolution of TOC dimensionless concentration during ozonation and photocatalytic ozonation with MWW effluent as aqueous matrix under simulated solar light radiation ( $\lambda=320-800$  nm) and all the catalysts studied